

# Research Journal of Pharmaceutical, Biological and Chemical Sciences

## Design, Synthesis, Aqueous Properties and Investigation of Novel Cationic Surfactants as A Long Term Green Corrosion Inhibitors Exposure

Magdy A-H Zahran<sup>1</sup>, Mohamed M. Mohammady<sup>2</sup>, Moneer M. Basuni<sup>3\*</sup>

<sup>1</sup>Chemistry Department, Faculty of Science, Moneufia University, Shebin El-Koam2323, Egypt

<sup>2</sup>Petroleum Application Department, Egyptian Petroleum Research Institute, Cairo11727, Egypt

<sup>3</sup>Nano Center for Materials Science, Zewail City of Science and Technology, 6th October City, 12588 Giza, Egypt

### ABSTRACT

A novel series of cationic surfactants namely: 1-(2-Aminoethyl)-2-octadecyl-imidazoline (A), N-Benzyl-N,N-dimethylaurayl -1-aminium chloride (B) and N-Benzyl-N,N-dimethylmyristyl -1-aminium chloride were synthesized, characterized and evaluated as a corrosion inhibitors. These prepared cationic surfactants possess very interesting physical properties such as good flow which make them suitable for the injection through the gas raw pipeline. The results showed that newly formulated surfactants prepared from A, B and C showed a good ability to act as water soluble types, no-foaming and stable film-persistent corrosion inhibitor for the thermodynamic-hydrodynamic corrosivity predictive models for the assessment of internal corrosion /erosion in the surface production pipelines (flow lines and gathering lines). Furthermore, the newly formulated showed strong antibacterial more than other commercial biocide samples.

**Keywords:** Fatty acid derivatives, gas pipelines, Corrosion inhibitor, protective films, Biocide.

*\*Corresponding author*

## INTRODUCTION

Corrosion is a major economic problem for all industrialized countries exist widely in various industrial fields, mainly in petroleum industrial resulting in huge economic losses[1]From 25 to 30% of the total economic losses in the oil and gas industry [2] so Corrosion has a very important economic impact in the petroleum industry[3] Several types of corrosive environments are encountered in the petroleum industry.CO<sub>2</sub> corrosion is recognized as a major factor for the failure of oil and gas pipe lines[4], Carbon dioxide (CO<sub>2</sub>) is a naturally occurring constituent in oil and gas production and is found in amounts varying from trace levels to as much as 50%. These problems have caused the consideration of many corrosion control methods and research in various oilfields around the world. The corrosion inhibitors can be classified in general, the inorganic inhibitors have cathodic actions or anodic. The organics inhibitors have both actions, cathodic and anodic and the protective by a film adsorption. the classification of the inhibitors shown on Fig. 2 [5]The application of corrosion inhibitors is one of the most effective and economical methods to protect metal represent flexible means of corrosion control in current and future, The need to produce and transport oil and gas under increasingly more severe operating conditions[6-9] In recent years, with improved recognition of environmental protection, development of green petroleum additives has received increasing attention, because the petroleum industry development needs to design new families of environmental of additives.[10-14] ,So Many inhibitor formulations have been developed for use in corrosion control. amines- and imidazolines-derivatives are extensively used as an active component in commercial corrosion inhibitor formulation and packages For its high efficiency and low toxicity, represent the most economical and effective ways[15-16] ,the quaternary salts of fatty acids on the imidazoline-type inhibitors, Imidazoline based corrosion inhibitors are well known to have high corrosion inhibitor activity in acidic medium caused by corrodents such as carbon dioxide other corrosive gases such as hydrogen sulfide in aqueous phase and therefore are used to minimize carbon dioxide induced oil and gas field corrosion[17,9]. Corrosion inhibitors based on organic substances are the most practical methods for protection of carbon steels mainly due to economic reasons [1-3].It is generally accepted that organic molecules inhibit corrosion via adsorption at the metal surface and form protective films, which can isolate the metal from corrosive medium. The mode of adsorption is dependent on the following factors: structure of the molecule, solution chemistry, characteristics of the metal surface and electrochemical potential at the interface. Such as functional group type, Four primary modes of adsorption are associated with organic compounds at surfaces: electrostatic adsorption, back bonding, chemisorption, and organometallic complex formation [3,7,18,19] fatty acids, amines, imidazolines, oxyalkylated amines, oxygen, sulphur or phosphorus containing species, quaternary amines) and long hydrocarbon chain (typically C<sub>14</sub> - C<sub>18</sub>) containing different polar hetero-atoms (N, O, P, or S) of high electron density and hydrophobes of long alkyl chains are efficient corrosion inhibitors. Polar hetero-atoms help them to chemisorb on metal surfaces resulting formation of protective surface complexes ,These inhibition processes involves the chemisorption of the nucleophilic heteroatom on the metal surface which in turn is shielded by the hydrophobes from the hostile aqueous medium[20,21].the imidazoline ring can adsorb on metal Fe surface by donating electrons to metal atoms and accepting electrons from 3dorbital of Fe atoms Some researchers believe they block the active sites and generate a barrier to reduce the transport of corrosive species to the metal surface, the mechanism of corrosion and adsorption of imidazoline on the surface of mild steel as showed in Fig. 2[22,23] Calculation of chemical adsorption energy between imidazolines and the Fe atom by quantum chemical methods was studied[24],Oleo imidazoline organic inhibitors work by this adsorption mechanism. The structural characteristic of inhibitor imidazoline film is greatly dependent on the structure of inhibitor molecule, such as functional group type and chain length, due to the impact of this groups on disperse, diffusion, solubility and adsorption of the imidazoline molecule. They are commonly used in conjunction with an acid at pH 4 or less in aqueous systems. Imidazoles have occupied a unique position in heterocyclic chemistry, and its derivatives have attracted considerable interests in recent years for their versatile properties in chemistry and biology. The imidazole derivatives possess extensive spectrum of biological activities such as antibacterial and antifungal [25-26]. Imidazoline derivative partially inhibits the formation of iron-oxidizing bacteria biofilm [27], Imidazolines will hydrolyze in water when present in the non-neutralized form so the prepared cationic imidazoline which act as cationic surfactant become more stable. These prepared cationic surfactants can adsorb on the metal surface through the formation protective film, some researchers believe that the mode stability of the adsorption film is dependent on structure of the molecule, some other researchers believe they also dependent on characteristics of the metal surface and electrochemical potential at the interface. However, there is few reports about the effect of flow velocity, slug flow, water condensate and sand production, under both of the current thermodynamic (temperature and pressure) and hydrodynamic (multiphase flow) operation conditions on the stability of the adsorption protective film.

In the present study we investigated the inhibition effect of A novel series of cationic surfactants for carbon steel corrosion in Multiphase flows, The focus of our current research was the Design, Synthesis, Aqueous Properties and Investigation of the quaternary ammonium salts of fatty acids (lauryl (C12), myristyl (C14) and oleyl : C18 unsaturated) as a long term corrosion inhibitors exposure in aggressive salt, sand and sludge contaminated aqueous solutions saturated with carbon dioxide at high flow rate and clay deposits.

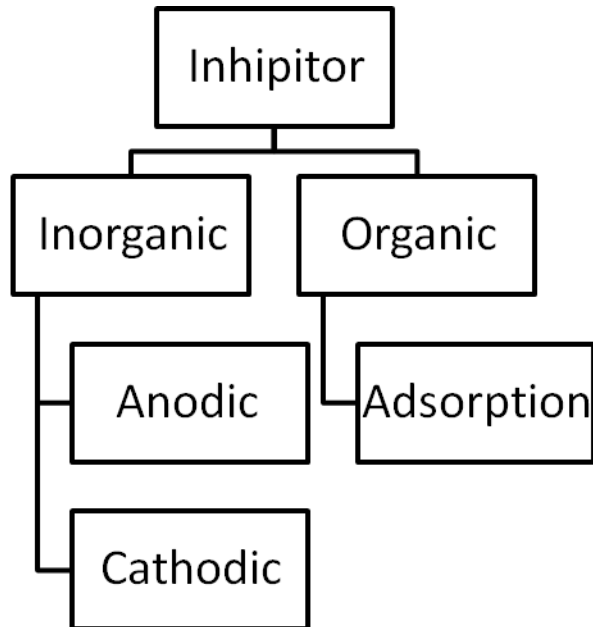


Figure 1: Classification of inhibitors.

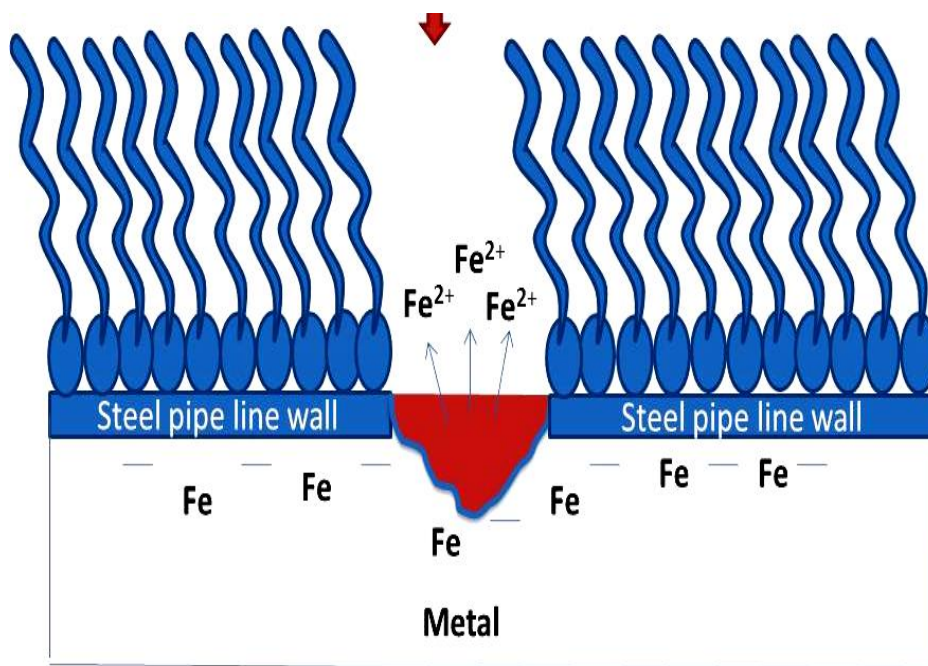


Figure 2: Sketch of adsorption of imidazoline corrosion inhibitor on corroding Fe surface.

**Nomenclature**

- PPM: Parts per million
- Mpy: Mils penetration per year
- MMSCFD: Million standard cubic feet per day

LPG: Liquefied petroleum gas  
OA: Oleic Acid  
DETA: Diethylenetriamine  
OIs: Oleic Imidazolines  
OA/DETA: Oleo Imidazoline Diethylenetriamine  
C12/C14 DMA: lauryl/myristyl Dimethyl amine  
CNG: Compressed natural gas  
AM: Antimicrobial Analysis  
PDMS: Polydimethylsiloxane  
BBLs: Barrels BBLs stands for Barrels  
CR: Corrosion rate

## Experimental and experimental methods

### Carbon steel

The chemical composition of carbon steel was the following 0.16 C, 0.26 Si, 1.30 Mn, 0.010 S, 0.009 P, 0.05 Nb, 0.026 Al, 0.007 Co, 0.013 Cu, 0.014 Cr and the remainder iron determined by an ARL™ 4460 Optical Emission Spectrometer (USA),

### Gas Production characteristics

Characteristics, Experimental conditions for corrosion measurements and Analytical data of the Assessment of internal corrosion in the surface production pipelines of the gas well indicate that the thermodynamic corrosivity predictive model has found that, under the thermodynamic operating conditions in the full length of the pipeline, the corrosivity of the flowing fluid due to carbon dioxide (0.4-0.5 mole%, 3.42-5.64 psi partial pressure) is rated as slightly corrosive with a possibility to cause general pitting to the carbon steel of the pipeline. The thermodynamic-Hydrodynamic prediction model established based on multiphase flow for the pipelines found that, for the whole length of the pipeline, the multiphase mixture flow velocity is always above both of the API-14E critical velocity and the service velocity limit for sand erosion, and therefore neither flow induced corrosion (erosion corrosion by liquid droplets impingement) nor sand erosion is predicted to occur.

### Weight Loss Techniques

The carbon steel sheets of 7 cm x 9.3 cm x 0.5 cm were sequentially abraded with different emery papers cleaned successively with distilled water, ethanol and acetone and finally dried in dry air at room temperature 25. After accurately weighing, the steel specimens were immersed in the CO<sub>2</sub>-saturated corrosion solution in 1000 mL PE bottles. The specimens were completely immersed for 12-120 h, with the addition of different concentrations of the synthesized cationic surfactant formula at 50 °C. The experiments were carried out in triplicate to get good reproducibility. The weight loss then was determined and the corrosion rate was expressed and the average value of the weight loss is reported. The specimens were sequentially abraded with different emery papers, degreased with acetone, washed with distilled water and dried. Corrosion parameters such as corrosion rate (CR) and inhibitor efficiency were calculated in the absence and presence of the cationic surfactant corrosion inhibitors at concentrations ranging from 50 to 200 ppm.

### Characterization

The FT-IR spectra of (C12/C14 DMA) and C12/C14 Dimethyl ammonium chloride were recorded using BRUCKER spectrophotometer using KBr pellet with spectrum of wave number range 4000–400 cm<sup>-1</sup> with an accuracy of 2 cm<sup>-1</sup>.

### Synthetic method

#### Preparation of oleo imidazoline

73.33 g (0.26 mols) of oleic Acid (OA) was placed in a 250 ml, 4-neck round bottomed flask equipped with an overhead stirrer, thermometer, addition funnel and a Dean-Stark trap. The (OA) was heated to 60° C in the presence toluene 30 as isotropic solvent. and then 26.67 g (0.25 mols) of Diethylenetriamine was added drop wise. The resulting mixture turned from light yellow to dark red with remarkable increase in viscosity and exothermed to 100° C to form ammonium salt neutralization. The mixture was then heated to 133°-143° C. for 3.5 hours to form amide. The hydrocarbon collected in the trap was returned to the flask. The mixture was thereafter heated to 160° C. for 1 hour while allowing water to collect in the Dean-Stark trap to completely of amid step. The resulting mixture was then heated at 165° C. for 2 hours and then at 240° C to allow to formation imidazoline ring OA/DETA imidazoline, for an additional hour during which time any further evolved water was collected. A nitrogen sweep was applied and the speed of the overhead stirrer was increased to facilitate removal of water. Following further heating of the mixture to 230° C. for an additional 1.5 hours, the reaction mixture was cooled and 50 g of the resulting oleo imidazoline 1-(2-Aminoethyl)-2-octadecyl-imidazoline was then reacted with 25 g of acetic acid which was carefully added dropwise to the imidazoline product to form cationic imidazoline. A temperature rise of about 70-89° C. was observed, Molecular structure of the prepared OA/DETA imidazoline, are shown in Fig. 3, the final products were investigated in this reaction. Following the progress of formation oleo-amid and oleo-imidazoline ring, average yield of oleo-amid and oleo-imidazoline ring will increase, accompanied by increase of water collecting in the Dean-Stark trap, Therefore the progress of amide and imidazoline ring OA/DETA imidazoline step could be reflected by the change amount of water to collect in the Dean-Stark trap to completely of final product.

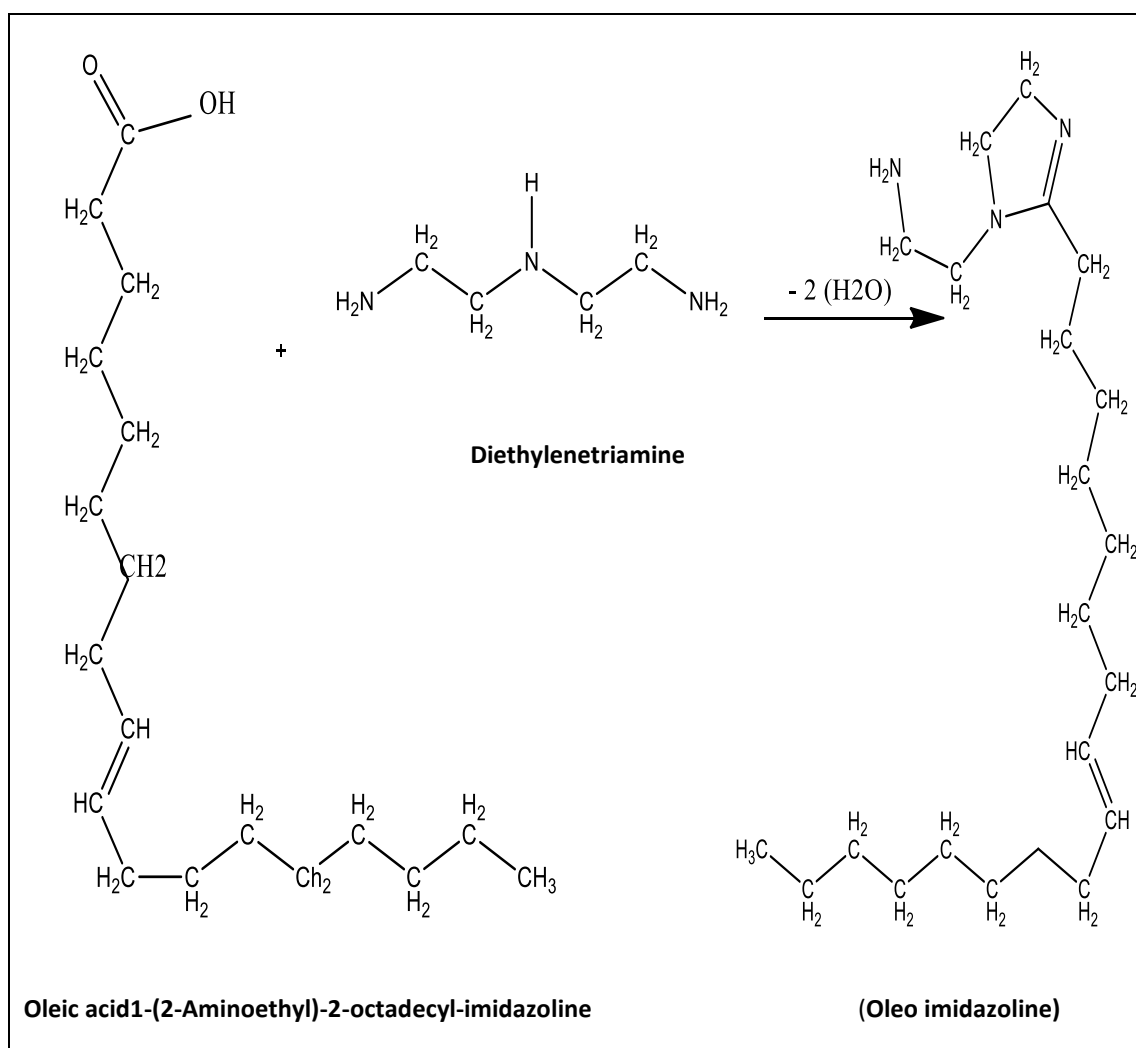


Figure 3: The Molecular structure of the prepared OA/DETA imidazoline

Preparation of a quaternized C12/C14 Dimethyl ammonium chloride

Place 190.47 grams represent one mull from C12/C14 dimethyl amine (30:70) and a magnetic stir bar into a 1000 ml 4-neck round bottomed flask that was partially submerged in controlled temperature water bath, a reflux condenser and equipped with magnetic stirrer, a nitrogen inlet thermometer and heater, Add 126.58 grams about one mull of Benzyl chloride to the flask with slowly addition. Stopper the flask tightly and heat its contents to 80° C. Maintain the temperature of the flask contents at 80° C. for 6 hours while stirring. The resulting product mixture will contain a high yield of quaternized C12/C14 DMA used as Biocide. the product is a nucleophilic substitution reaction of alkyldimethylamine with benzyl chloride [27], General Molecular structure of prepared cationic surfactants mixture from N-Benzyl-N,N-dimethylaurayl -1-aminium chloride and N-Benzyl-N,N-dimethylcetyl -1-aminium chloride can be seen in Fig. 4

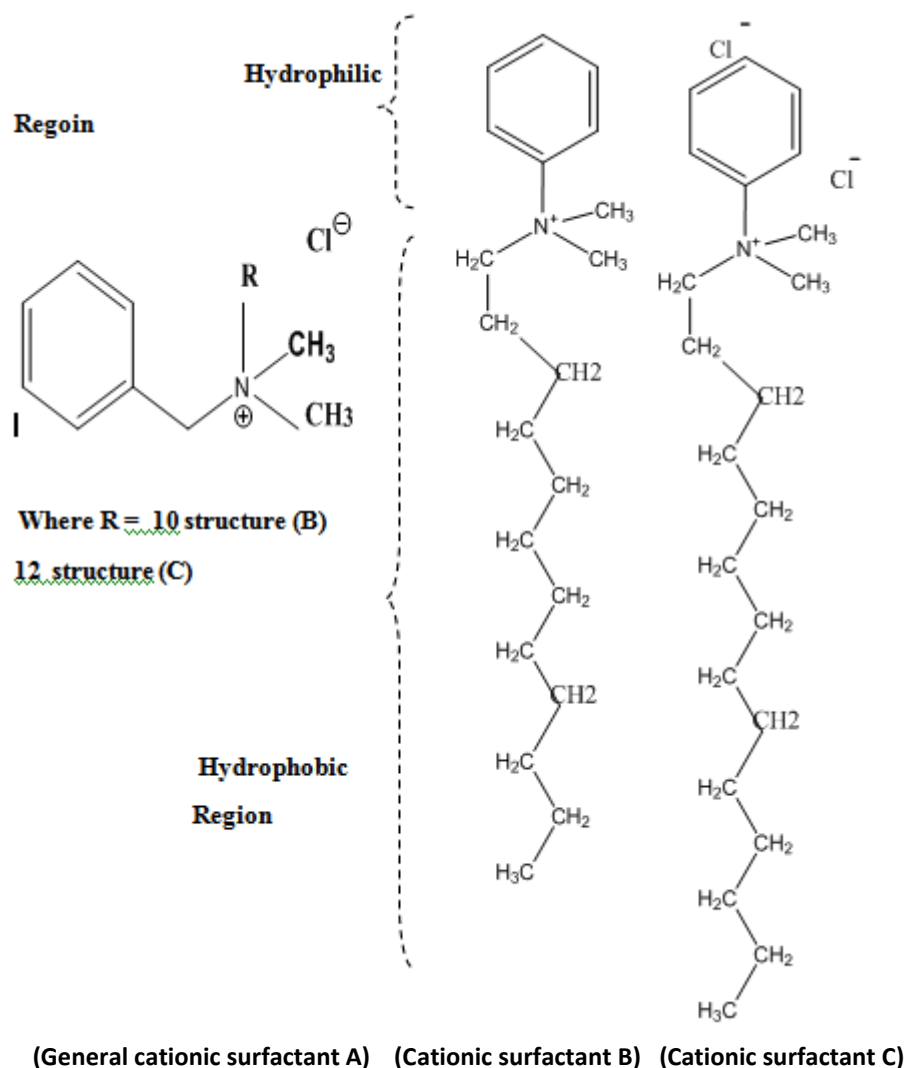


Figure 4: The molecular structure of the synthesized quaternary ammonium salts (C12/C14 Dimethyl ammonium chloride).

#### Preparation of Quaternary amine-cationic imidazoline corrosion inhibitor formula

For preparation of water soluble, no-foaming, stable film-persistent corrosion inhibitor adequate for WASCO line field trial the prepared newly formulation contained A novel series of cationic surfactants namely: 1-(2-Aminoethyl)-2-octadecyl-imidazoline (A), N-Benzyl-N,N-dimethylaurayl -1-aminium chloride (B), N-Benzyl-N,N-dimethylcetyl -1-aminium chloride in addition to polydimethylsiloxane (EBCABURST-200) and Hydrazine. compound (A) is acationicimidazoline OA/DETA imidazoline (oleo imidazolineDiethylenetriamine) main companionant corrosion inhibitor, C12/C14 Dimethyl amine quaternary Benzyl chloride as biocide, antifoam silicon base (EBCABURST-200), solvent (iso propanol) and Hydrazine which have an important role in corrosion inhibitor formula by neutralizing acidic carbon dioxide or by shifting surface pH towards less acidic and corrosive values. in



general amines such as morpholine, hydrazine, ethylene amine or diethylenetriamine are transported with gas steam to prevent corrosion in the condenser tubes.

**RESULT AND DISCUSSION**

**Aqueous properties, analytical data and antimicrobial study for C12/C14 dimethyl ammonium chloride against microorganisms**

Bacteria Controlled Environment Against both aerobic and anaerobic microorganisms is needed in Corrosion, including injection and work over fluids. Many cationic emulsifiers such as quaternized C12/C14 Dimethyl ammonium chloride have multifunctional properties enable them to use as corrosion inhibitor, sulphurous and oxygen scavenger, oil-wetting agents, ph adjuster , demulsifier/sludge breaker for enhanced oil extraction and Provides supplemental emulsion stability in oil emulsions at high different temperatures [29-33], it is safe, rapid and acting as bactericide, algacide , fungicide [34] .it is have powerful antimicrobial activity at low dosage (ppm), it is also Compatible with Non-ionic, Ampholytic and Cationic surface-active agents. The greatest biocidal activity due to their cationic amphiphilic property, having a distinct hydrophobic and hydrophilic region, resulting from nucleophilic substitution of alkyl dimethylamine and benzyl chloride, quaternized C12/C14 Dimethyl ammonium chloride hydrophilic cationic region destabilizes the pathogen's surface, mechanism of bactericidal/microbicidal action is thought to be due to disruption of intermolecular interactions. This can cause dissociation of cellular membrane lipid bilayers, which compromises cellular permeability controls and induces leakage of cellular contents. by forming electrostatic interactions with negatively charged components .The effect of quaternized C12/C14 Dimethyl ammonium chloride is to damage the pathogen's membrane, thus for bacteria, disrupting essential cell processes like ATP synthesis or solute uptake [35,36,37] in addition to enzyme disorder and lack of protein synthesis. This series is involved in the comparative study between quaternized C12/C14 Dimethyl ammonium chloride and some other commercial Biocide samples such as MERGAL® and ISOCINRR14 .the results showed in Table 1. indicate that Quaternized C12/C14 Dimethyl amine showed strong antibacterial more than other commercial biocide samples MERGAL® and ISOCINRR14 the prepared cationic surfactant C12/C14 Dimethyl ammonium chloride have Extreme effect on microorganisms (Escherichia coli ATCC13706, Pseudomonas aeruginosa ATCC15442, Listeria monocytogenes ATCC25152 Staphylococcus aureus ATCC6538), Thus can be used as antimicrobial in the newly corrosion inhibitors formulation. in addition to their compatible with nonionic, ampholytic and cationic surface active agents .so It is widely used in many other formulations such as cleaner , sanitizers for dairy industry , food storage, cosmetics, pharmaceutical and paints . The their Antimicrobial activity of C12/C14 Dimethyl amine showed in Table 1

Samples	Tested bacterial strains			
	E.Coli ATCC13706	Pseudomonas aeruginosa ATCC15442	Listeria monocytogenes ATCC25152	Staphylococcus aureus ATCC6538
MERGAL®	++	+++	++	++
ISOCINRR14	+++	+++	++	++
C12/C14 DMA Q.bcl	++++	++++	++++	+++

Where \*(++) Moderate effect on microorganisms; \*(+++) High effect on microorganisms; \*(++++) Extreme effect on microorganisms

**Characterization FT-IR spectra of C12/C14 Dimethyl ammonium chloride**

The FT-IR spectra of C12/C14 Dimethyl amine (C12/C14 DMA) and Quaternized C12/C14 Dimethyl amine are shown in Fig. 6. and Fig. 7. The spectrum of C12/C14 DMA shows a broad band at 3439 cm<sup>-1</sup> that can be assigned to the stretching vibration of N H groups. The bands at 2923 cm<sup>-1</sup> and 2851 cm<sup>-1</sup> correspond to C H stretching of aliphatic group, the absorption band at 1644 cm<sup>-1</sup> can be attributed to the CN stretching in amine groups. The N H bending in amine groups were observed obviously at 1550 cm<sup>-1</sup>. Other major bands observed in Cs were found at 1380 cm<sup>-1</sup> (amine III band, CN stretching vibration), 1314 cm<sup>-1</sup> (CN stretching vibration), 1152 cm<sup>-1</sup>. The FT-IR spectrum of Quaternized C12/C14 dimethyl ammonium chloride shows all the significant characteristic bands of both (C12/C14 DMA) and benzyl chloride with shifts in the position of the bands. Some

bands were shifted to longer wavenumbers such as the band at 858cm<sup>-1</sup>of (C12/C14 DMA) to 878 cm<sup>-1</sup> and the bands at 1442 cm<sup>-1</sup>and 1103 cm<sup>-1</sup>of (C12/C14 DMA) were shifted to1455 cm<sup>-1</sup>and 1106 cm<sup>-1</sup>, respectively. On the other hand, other bands were shifted to shorter wavenumbers such as the bands at1652 and 1033 cm<sup>-1</sup>of Cs to 1634 and 1022 cm<sup>-1</sup>, respectively. The broadening and the shifting of the latter band can be assigned to the electrostatic forces between the moieties of (C12/C14 DMA) and benzyl chloride. In accordance with the aforementioned IR results, it can be concluded the electrostatic forces are the driving forces for the interaction between the moieties of (C12/C14 DMA) and benzyl chloride which indicate that formation of quaternary ammonium salt.

**Table 2: Physical Properties of prepared a quaternized C12/C14 dimethyl amine (Q.bcl) compound**

Items	Index
Appearance	Colorless to yellowish transparent liquid
Active content %	80%
Amine salt %	1.0
PH(1% water solution)	7.0
Density	0.97(±0.01) g/ML

**Aqueous properties and analytical data of defoamer EBCA BURST-200**

Polydimethylsiloxane (PDMS oil) widely used in many industrial application as defoaming agent, their hydrophobically modified particles are dispersed in the oil to increase antifoam efficiency [38] EBCABURST-200 is Highly efficient silicone polydimethylsiloxane emulsified by mixture of high and low HLB nonionic emulsifiers, used as defoamer in the newly our corrosion inhibitor formula this defoamer have efficient and stable in wide temperature range, effective in all types of processing equipments, leaving no scum and Avoid spots on internal surface of production pipelines, also This product have sufficiently stable to shear, chemicals, temperature and pH to prevent effects such as scum formation, silicone accumulation. EBCABURST-200 is the suitable product. Unlike many other silicone defoamers, EBCABURST-200 is stable in baths containing high concentrations of electrolytes from a variety of sources in addition of all EBCABURST-200 can be mixed well with any of corrosion formula, also can be dilute at the use by amount 5 times with water before adding it to the formula in the other hand, Silicone Polymers ready to biodegradation in nature by soil microorganisms [39,40]which make it the suitable type in green corrosion inhibitor formula. The needed to defoamer because almost of quaternary ammonium compound formed a huge foams in aqueous media during the filling in the chemical skid and injection.

**Table 3: Aqueous properties and Analytical Data of Silicon base Defoamer EBCA BURST-200**

Property	EBCABURST-200
Appearance	Opaque white liquid
Chemical	Silicon emulsion
Ionic charge	Nonionic
PH	7 – 8
Concentration level	High

**Aqueous properties and Analytical Data of quaternary amine-cationic imidazoline corrosion inhibitor formula**

Aqueous properties Analytical Data samples of Quaternary amine-cationic imidazoline water soluble type, no-foaming, stable film-persistent corrosion inhibitor formula for raw gas Production with associated water and its properties at the solution/air interface were investigated by measuring dynamic viscosity (Cp) at low and pediment temperatures, Pour point(°C), density at 40°C, Refractive index at 20°C and pH using standard test methods are shown in table 4


Which indicate that Quaternary amine-cationic imidazoline corrosion inhibitor have optimum properties for the filling in the chemical skid during field trials corrosion inhibitor long term exposure. The evaluate fluid properties have an important role in the recommended dosage for each well field trial conditions to customize a



corrosion-treatment program specific to The chemical injection rate optimized needs. Further investigation was conducted based on FTIR spectra for three sample called EW#3, Bassoat -3 and Bassant #1 samples corrosion inhibitor three samples were prepared almost identical which shown in

**Table 4: Result of analysis for corrosion inhibitor Bassant #1well**

Experiment	Method	Result
Dynamic viscosity, cp, @ 15°C	ASTM D-445	37.0
Dynamic viscosity, cp, @ 25°C		22.8
Pour point, °C	ASTM D- 97	-15
pH		7.21
Density @ 40°C	ASTM D-1298	0.9975
Refractive index @ 20°C	ASTM D-1218	1.424

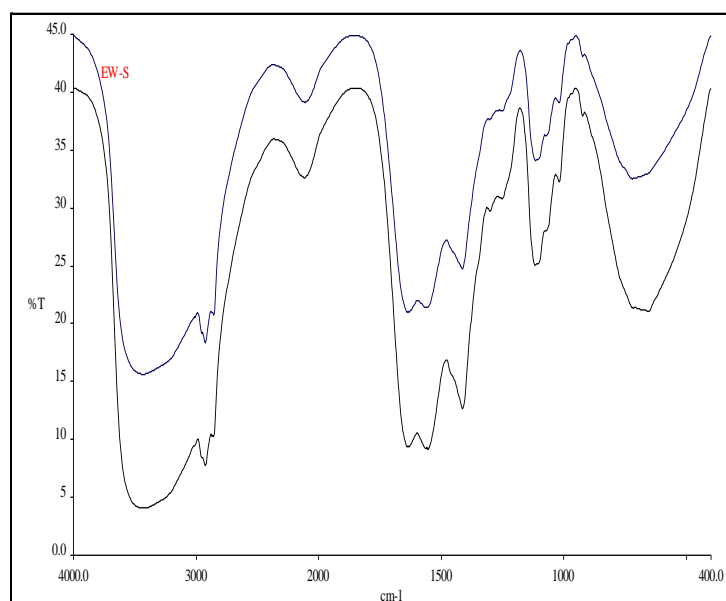

**Figure 5: FTIR spectra corrosion inhibitor sample from EW-5 and Bassoat -3 batch**

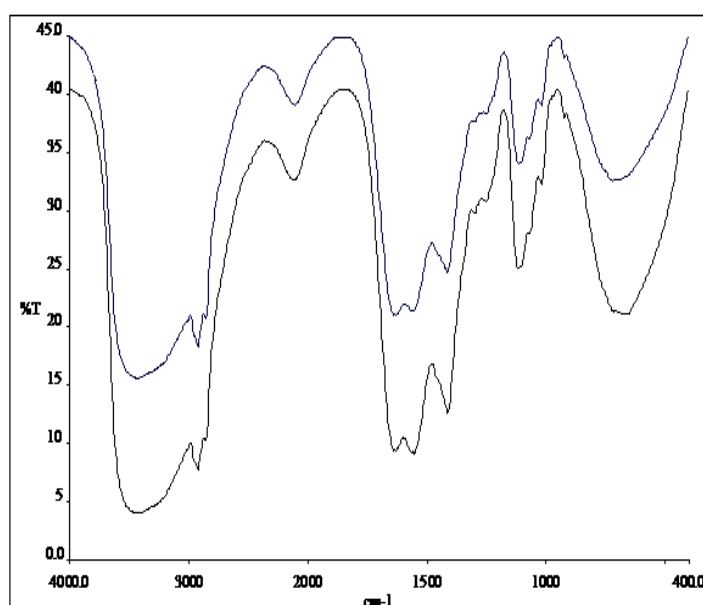


Figure 6: FTIR spectra corrosion inhibitor sample from EW-5 and Bassant #1 samples


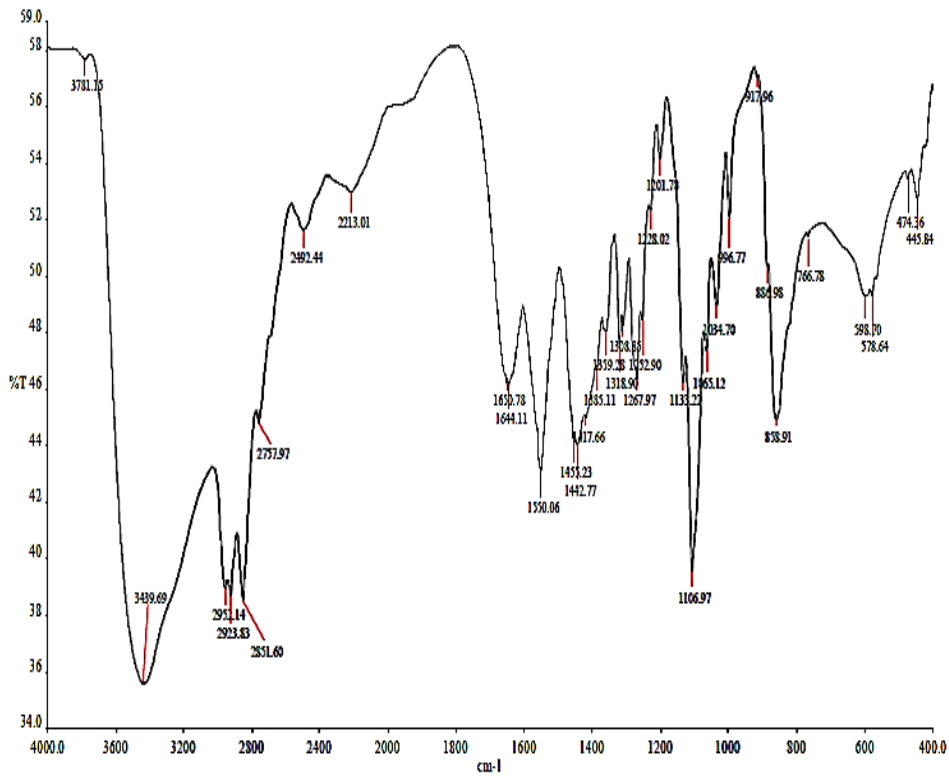


Figure 7: FTIR spectra C12/C14 DMA

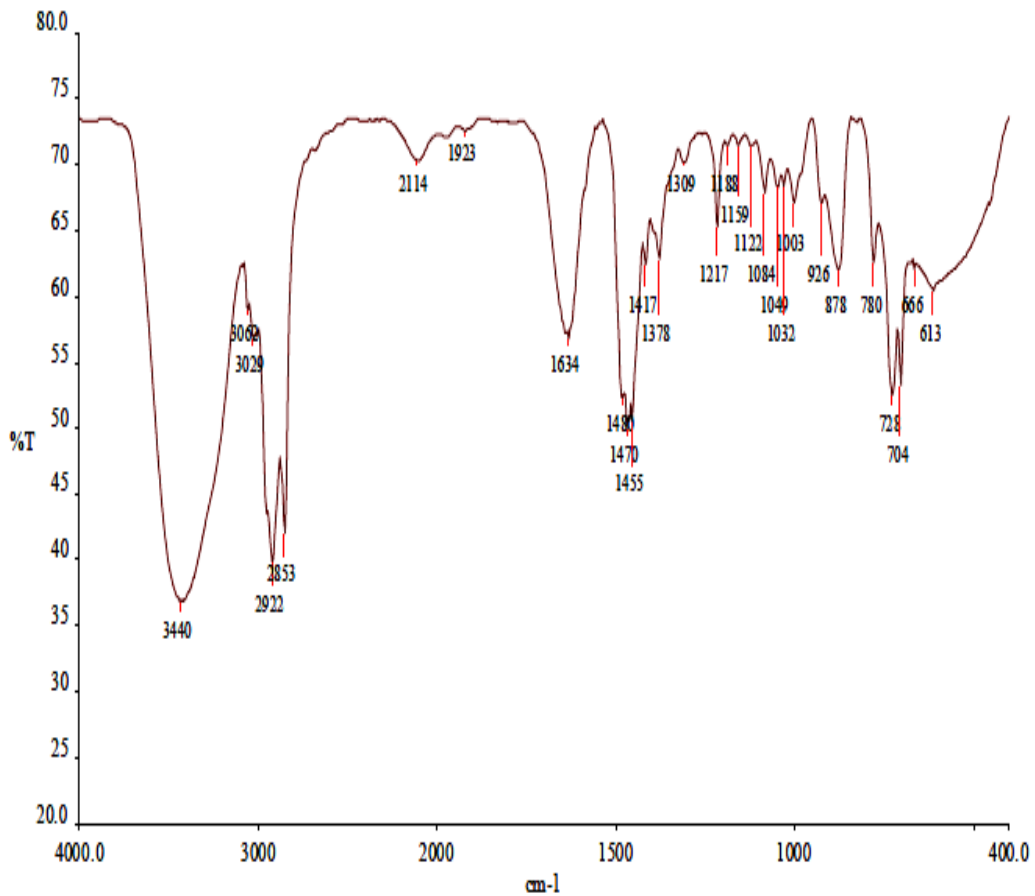

**Figure 8: FTIR spectra of cationic C12/C14 DMA  
Laboratory Evaluation of Quaternary amine-cationic imidazoline corrosion inhibitor**

Imidazoline derivatives, a kind of environmental-friendly corrosion inhibitors, can effectively inhibit metals corrosion in CO<sub>2</sub> environment. Corrosion test have been carried out in formation water at 50 °C is shown in Table 7. In the absence and presence of inhibitor using static and linear polarization (L.P) methods. The Table 7 clearly shows that the inhibition efficiencies increased with the increasing concentration at 50°C, suggesting that OA/DETA imidazoline forms an inhibitive film on the metal Fe surface. [41] The increasing number of molecules of inhibitor covering the surface area of metal with the increase of its concentration resulted in a decrease of the corrosion rate and increase of inhibition efficiency. Generally it is assumed that the first step of the inhibition of aggressive media is the adsorption mechanism of the inhibitor at the metal/solution interface. Some types of adsorption of organic molecules at the metal/solution interface are mentioned by the following: (1) electrostatic interaction between the charged metal and the charged molecules, (2) interaction of uncharged electrons pairs in the inhibitor molecule with the metal surface, (3) interaction of π-electrons with the metal and (4) combination of (1) and (3) [42,43]. The newly formula represent an environmental alternatives and effective for the protection of metallic surfaces against corrosion, adsorption of used compounds was found to obey Langmuir isotherm [44,45].

**Table 5: Laboratory Evaluation of Quaternary amine-cationic imidazoline corrosion inhibitor**

Method	Blank Corr. Rate, mpy	% Inhibition, at:		
		50	100	200 ppm
Static	2.3	28	54	36
L.P	49	-47	16	12

**Investigation of Oleo Imidazoline as Long Term Corrosion Inhibitor Exposure (CORRICHEM field trial)**

Conclusion of Corrosion inhibitor CORRICHEM field trial, Concerning start up Quaternary amine-cationic imidazoline Corrosion Inhibitor the chemical injection skids of EW-5, Bassant #1 and Bassoat-3 wells were filled with batch treatment (140 Lt/ 24 hours at EW-5, Bassant #1 and (100LT/ 24hours at Bassoat -3 and the chemical injection rate optimized to (2 Pint/Day; based on each well production) as continues treatment injection and the coupons had been installed for at injection 2 pint/MMMSCF for 30 day (total trial day). The carbon steel coupons are weighted and installed for the trilled wells at the end of each flow line. The cleaning and calculations for coupons were done by lab staff and the results are shown in Table 8. which indicate that the efficiency of corrosion inhibitor CORRICHEM the corrosivity fluids being currently handled in the surface production pipelines (flow lines and gathering lines ) of the gas wells depend on the chemical and physical properties of the produced gas, water condensate and sand production, under both of the current thermodynamic (temperature and pressure) and hydrodynamic (multiphase flow) operation conditions in these pipes. Where that the newly formulation CORRICHEM compound showed a good efficiency as corrosion inhibitor in both EW-5 and Bassoat -3 well, and moderate in Bassant #1 the reason should be attributed to the increasing of flow rate in the last well Bassant #1 well which causes the great internal corrosion/erosion in the surface production pipelines. The flow enhanced corrosion which is associated with slug flow, slug flow can drastically cause severe corrosion in pipes by removing the protective film on wall of the pipe there about by the shear forces caused by the high turbulent mixing zone of the slug which develops region of high shear forces in the slug which can destroy the boundary layer close to the wall. This situation causes the stripping off the protective layer present on the metal surface of the pipe wall by slug, which in turn leads to increase in corrosion rates. Also this situation makes the formation a stable inhibitor film difficult and the slug flow thus drastically reduce the effectiveness of the corrosion inhibitor films. The slug flow could occur at any orientation of the pipe depending on the inclination angle, altitude, topography and geometry relation to the pipe. Therefore, flow enhanced corrosion could take place at Bassant O'clock positions depending on where the slug is exerting shear to the well of the pipe. So the main concern with the flow enhanced corrosion associated with the intermittent slug flow regime is that, this corrosion form could result in the penetration of the wall of the pipelines.

**Table 6: Field trial Quaternary amine-cationic imidazoline corrosion inhibitor Evaluation**

Well Name	Average Corrosion Rate (MPY)	Corrosion rate	Status
EW-5	0.0524 (low)	LOW	Technically Accepted
Bassoat-3	0.2989	LOW	Technically Accepted
Bassant #1	1.3575	Moderate	Not Technically Accepted

### CONCLUSIONS

A series of quaternary ammonium salts were successfully synthesized and characterized by FTIR, Surfactant C12/C14 Dimethyl ammonium chlorides have been obtained with good yield after short reaction times in the presence methanol as solvent. Properties of these prepared cationic surfactant, including Dynamic viscosity, Pour point, pH, density, melting points, solubility and antimicrobial activity have an important role for the injection through the gas raw pipeline gas The results showed that newly formulated showed good corrosion inhibitors for production pipelines in oil and gas wells applications. The inhibition efficiency of these prepared cationic surfactants increases with increasing the concentration at 50°C. The efficiency of corrosion inhibitor corrichem in the surface production pipelines of the gas wells depend strongly on the chemical and physical Properties of the produced gas, water condensate, clay deposits and sand production under both of the current thermodynamic and hydrodynamic operation conditions in these pipes, The addition of antimicrobial agents have an important role in formulation of long term Corrosion Inhibitor exposure increase amines and their derivatives molecules in formulation lead to the increase antimicrobial activity and long term storage [46,47].

However, more work is required, both to better understand the potential scope of their properties and to broaden the range of materials in this family of salts to become make strong adsorption on inner surface of production pipelines gas well at high flow rate in the presence slug flow to decrease and control corrosion/erosion in the surface of production pipelines.

### ACKNOWLEDGMENTS

The authors would like to express their gratitude to EBCA R&D petroleum center, Egyptian British co., EGYPT. The authors would also like to thank to Dr. Waseam A. Hassan, Dr. Tarek E. Salem and National Research Center service for virus researches and Bioassays., Egypt. for helping in the antimicrobial analysis (AMA).

### REFERENCES

- [1] Tiu, Brylee David B., and Rigoberto C. Advincula. "Polymeric corrosion inhibitors for the oil and gas industry: design principles and mechanism." *Reactive and Functional Polymers* 95 (2015): 25-45
- [2] R.N. Butler, J.D. Thornton, P. Moynihan, *J. Chem. Res. (S)* (1981) 84.
- [3] Tiu, B.D.B. and Advincula, R.C., 2015. Polymeric corrosion inhibitors for the oil and gas industry: design principles and mechanism. *Reactive and Functional Polymers*, 95, pp.25-45.
- [4] Zhang, H.H., Pang, X., Zhou, M., Liu, C., Wei, L. and Gao, K., 2015. The behavior of pre-corrosion effect on the performance of imidazoline-based inhibitor in 3wt. %NaCl solution saturated with CO<sub>2</sub>. *Applied Surface Science*, 356, pp.63-72.
- [5] Camila G. Dariva and Alexandre F. Galio, 2014. *Corrosion Inhibitors – Principles, Mechanisms and Applications, Developments in Corrosion Protection*, Dr. M. Aliofkhaezrai (Ed.), ISBN: 978-953-51-1223-5, InTech.
- [6] Liu, J., Yu, W., Zhang, J., Hu, S., You, L. and Qiao, G., 2010. Molecular modeling study on inhibition performance of imidazolines for mild steel in CO<sub>2</sub> corrosion. *Applied Surface Science*, 256(14), pp.4729-4733.
- [7] Yan, Y., Wang, X., Zhang, Y., Wang, P., Cao, X. and Zhang, J., 2013. Molecular dynamics simulation of corrosive species diffusion in imidazoline inhibitor films with different alkyl chain length. *Corrosion Science*, 73, pp.123-129.

- [8] Li, X., Deng, S. and Fu, H., 2011. Benzyltrimethylammonium iodide as a corrosion inhibitor for steel in phosphoric acid produced by dihydrate wet method process. *Corrosion Science*, 53(2), pp.664-670.
- [9] Edwards, A., Osborne, C., Webster, S., Klenerman, D., Joseph, M., Ostovar, P. and Doyle, M., 1994. Mechanistic studies of the corrosion inhibitor oleic imidazoline. *Corrosion Science*, 36(2), pp.315-325.
- [10] Cui, R., Gu, N. and Li, C., 2011. Polyaspartic acid as a green corrosion inhibitor for carbon steel. *Materials and Corrosion*, 62(4), pp.362-369.
- [11] Abdel, M., Zahran, H. and Basuni, M.M., 2015. Study on Graft-Copolymerization of Sodium Lignosulfonates with Acrylic Monomers. *KGK-KAUTSCHUK GUMMI KUNSTSTOFFE*, 68(9), pp.35-40.
- [12] Magdy A. Zahran, Mohammed M. Mohamdy, Moneer M. Basuni, Study on Lignin Graft Copolymer as Additive agent for the Hydrocarbon Drilling industry, *International Journal of Advanced Scientific and Technical Research* 2014; 4(4) pp.916-932.
- [13] Zahran, M.A. and Basuni, M.M., 2014. PREPARATION AND EVALUATION OF SOME LIGNIN GRAFT COPOLYMERS AND THEIR APPLICATION IN DRILLING FLUID. *International Journal of Academic Research*, 6(3).
- [14] Zahran, M.A., Abd El-Mawgood, W.A. and Basuni, M.M., 2016. Poly Acrylic Acid: Synthesis, aqueous Properties and their Applications as scale Inhibitor. *KGK-KAUTSCHUK GUMMI KUNSTSTOFFE*, 69(7-8), pp.53-58.
- [15] Zhang, K., Xu, B., Yang, W., Yin, X., Liu, Y. and Chen, Y., 2015. Halogen-substituted imidazoline derivatives as corrosion inhibitors for mild steel in hydrochloric acid solution. *Corrosion Science*, 90, pp.284-295
- [16] Zhang, J., Qiao, G., Hu, S., Yan, Y., Ren, Z. and Yu, L., 2011. Theoretical evaluation of corrosion inhibition performance of imidazoline compounds with different hydrophilic groups. *Corrosion Science*, 53(1), pp.147-152.
- [17] Lusk, D., CASSERLY, T., GUPTA, M., BOINAPALLY, K. and CAO, Y., 2008. Armoured against corrosion. *Hydrocarbon engineering*, 13(11) pp. 115-118
- [18] Dougherty, J.A., 2004, January. Aggressive agents as corrosion inhibitors in gas and oil production. In *Corrosion 2004*. NACE International.
- [19] Babic-Samardzija, K., Lupu, C., Hackerman, N., Barron, A.R. and Luttge, A., 2005. Inhibitive properties and surface morphology of a group of heterocyclic diazoles as inhibitors for acidic iron corrosion. *Langmuir*, 21(26), pp.12187-12196.
- [20] Jawich, M.W., Oweimreen, G.A. and Ali, S.A., 2012. Heptadecyl-tailed mono-and bis-imidazolines: A study of the newly synthesized compounds on the inhibition of mild steel corrosion in a carbon dioxide-saturated saline medium. *Corrosion Science*, 65, pp.104-112.
- [21] V. Jovancicevic, S. Ramachandran, P. Prince, Inhibition of carbon dioxide corrosion of mild steel by imidazolines and their precursors, *Corrosion* 55(1999) 449-455.
- [22] Zuo, J., Guo, F., Zhu, J., Chen, A., Hu, Y., Lin, C. and Jiang, C., 2015. Effects of benzotriazole on the magnesium phosphate coating. *Applied Surface Science*, 359, pp.166-171.
- [23] Chaudhry, A.U., Mittal, V. and Mishra, B., 2015. Nano nickel ferrite (NiFe<sub>2</sub>O<sub>4</sub>) as anti-corrosion pigment for API 5L X-80 steel: An electrochemical study in acidic and saline media. *Dyes and Pigments*, 118, pp.18-26.
- [24] Wang, D., Li, S., Ying, Y., Wang, M., Xiao, H. and Chen, Z., 1999. Theoretical and experimental studies of structure and inhibition efficiency of imidazoline derivatives. *Corrosion Science*, 41(10), pp.1911-1919.
- [25] Verma, A., Joshi, S. and Singh, D., 2013. Imidazole: Having versatile biological activities. *Journal of Chemistry*, 2013.
- [26] Wani, M.Y., Ahmad, A., Shiekh, R.A., Al-Ghamdi, K.J. and Sobral, A.J., 2015. Imidazole clubbed 1, 3, 4-oxadiazole derivatives as potential antifungal agents. *Bioorganic & medicinal chemistry*, 23(15), pp.4172-4180.
- [27] Liu, H., Gu, T., Zhang, G., Wang, W., Dong, S., Cheng, Y. and Liu, H., 2016. Corrosion inhibition of carbon steel in CO<sub>2</sub>-containing oilfield produced water in the presence of iron-oxidizing bacteria and inhibitors. *Corrosion Science*, 105, pp.149-160.
- [28] Pernak, J., Mirska, I. and Kmiecik, R., 1999. Antimicrobial activities of new analogues of benzalkonium chloride. *European journal of medicinal chemistry*, 34(9), pp.765-771.
- [29] Negm, N.A., El Farargy, A.F., Al Sabagh, A.M. and Abdelrahman, N.R., 2011. New Schiff base cationic surfactants: surface and thermodynamic properties and applicability in bacterial growth and metal corrosion prevention. *Journal of Surfactants and Detergents*, 14(4), pp.505-514.

- [30] Negm, N.A. and Morsy, S.M., 2005. Corrosion inhibition of triethanolammonium bromide mono-and dibenzoate as cationic inhibitors in an acidic medium. *Journal of surfactants and detergents*, 8(3), pp.283-287.
- [31] Negm, N.A. and Morsy, S.M., 2005. Corrosion inhibition of triethanolammonium bromide mono-and dibenzoate as cationic inhibitors in an acidic medium. *Journal of surfactants and detergents*, 8(3), pp.283-287.
- [32] Negm, N.A. and Aiad, I.A., 2007. Synthesis and characterization of multifunctional surfactants in oil-field protection applications. *Journal of surfactants and detergents*, 10(2), pp.87-92.
- [33] Shehata, H.A., El-wahab, A.A., Hafiz, A.A., Aiad, I. and Hegazy, M.A., 2008. Syntheses and characterization of some cationic surfactants. *Journal of Surfactants and Detergents*, 11(2), pp.139-144.
- [34] Hegazy, M.A., El-Etre, A.Y., El-Shafaie, M. and Berry, K.M., 2016. Novel cationic surfactants for corrosion inhibition of carbon steel pipelines in oil and gas wells applications. *Journal of Molecular Liquids*, 214, pp.347-356.
- [35] Coughlin, R.T., Tonsager, S. and McGroarty, E.J., 1983. Quantitation of metal cations bound to membranes and extracted lipopolysaccharide of *Escherichia coli*. *Biochemistry*, 22(8), pp.2002-2007.
- [36] Fazlara, A. and Ekhtelat, M., 2012. The disinfectant effects of benzalkonium chloride on some important foodborne pathogens. *American-Eurasian Journal of Agricultural & Environmental Science*, 12(1), pp.23-29.
- [37] McDonnell, G. and Russell, A.D., 2001. Antiseptics and disinfectants: Activity, action, and resistance. *Clinical microbiology reviews*, 14(1), p.227.
- [38] Bergeron, V., Cooper, P., Fischer, C., Giermanska-Kahn, J., Langevin, D. and Pouchelon, A., 1997. Polydimethylsiloxane (PDMS)-based antifoams. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 122(1), pp.103-120.
- [39] Lehmann, R.G., Miller, J.R. and Collins, H.P., 1998. Microbial degradation of dimethylsilanediol in soil. *Water, Air, and Soil Pollution*, 106(1-2), pp.111-122.
- [40] Lehmann, R.G., Miller, J.R. and Collins, H.P., 1998. Microbial degradation of dimethylsilanediol in soil. *Water, Air, and Soil Pollution*, 106(1-2), pp.111-122.
- [41] Jevremović, I., Singer, M., Nešić, S. and Mišković-Stanković, V., 2013. Inhibition properties of self-assembled corrosion inhibitor talloildiethylenetriamineimidazoline for mild steel corrosion in chloride solution saturated with carbon dioxide. *Corrosion Science*, 77, pp.265-272.
- [42] Gogoi, P.K. and Barhai, B., 2011. Corrosion Inhibition of Carbon Steel by a Multi-component Blend Containing Zinc Diethyldithiocarbamate Complex in Combination with Trisodium Orthophosphate. *Int. J. Electrochem. Sci*, 6, pp.136-145.
- [43] Akbarzadeh, E., Ibrahim, M.M. and Rahim, A.A., 2011. Corrosion inhibition of mild steel in near neutral solution by kraft and soda lignins extracted from oil palm empty fruit bunch. *Int. J. Electrochem. Sci*, 6(11), pp.5396-5416.
- [44] Azzam, E.M.S., Hegazy, M.A., Kandil, N.G., Badawi, A.M. and Sami, R.M., 2015. The performance of hydrophobic and hydrophilic moieties in synthesized thiol cationic surfactants on corrosion inhibition of carbon steel in HCl. *Egyptian Journal of Petroleum*, 24(4), pp.493-503.
- [45] Al-Sabagh, A.M., Nasser, N.M., Farag, A.A., Migahed, M.A., Eissa, A.M. and Mahmoud, T., 2013. Structure effect of some amine derivatives on corrosion inhibition efficiency for carbon steel in acidic media using electrochemical and quantum theory methods. *Egyptian Journal of Petroleum*, 22(1), pp.101-116.
- [46] Yahiya. A. Youssef a, Waseam. A. Hassan b, Salah. M. El-Kousy, Mohammed. A. Tawila, Moneer M. Basuni, 2016. Synthesis, Characterization and Aqueous Properties of a polymerisable nonionic surfactant Exposure, *Research Journal of Pharmaceutical, Biological and Chemical Sciences* 7(5) pp.2650-2664 .
- [47] M. A. H.Zahran, Osman, A. M. A., Wahed, R. A., Attia, M., Pedersen, E. B., Elnasser, G. A., Turky, A. S. 2015. Design, synthesis and antimicrobial evaluation of novel carbendazim dithioate analogs. *Research Journal of Pharmaceutical, Biological and Chemical Sciences*, 6(4), pp. 1084-1092.